

## Use of High Strength Structural Bolting Assemblies for Preloading BS EN 14399-7 PC 8.8 Csk with Direct Tension Indicators (DTI's)


**NOTE:** BS EN 14399-7 Countersunk head bolting assemblies are not stock items and it is strongly recommended that their availability is ascertained before they are specified for a connection.

### **Assembly Configuration**

The standard assembly configuration for BS EN 14399-7 property class 8.8 countersunk head bolting assemblies shall consist of the following:-

- a) BS EN 14399-7 property class 8.8 countersunk head bolt (marked 8.8 HR)
- b) Direct tension indicator (marked H8) (component identified as 1 below)
- c) Nut face washer (marked HN) (component identified as 2 below)
- d) BS EN 14399-3 property class 10 nut (marked 10 HR)

The components shall be assembled as shown below with the bolt placed in the steelwork and at the other side of the connection the direct tension indicator is fitted with the flat side against the steelwork and the indicator protrusions facing outwards. The nut face washer is fitted over the bolt threads so that it sits on top of the indicator protrusions and the nut is assembled with the side containing the marking facing outwards and the smooth unmarked side of the nut against the nut face washer.

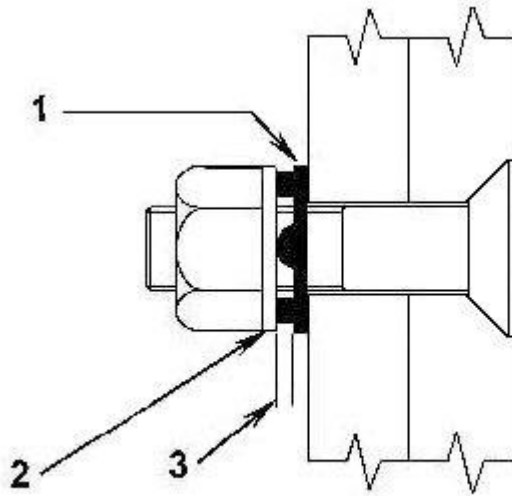

**KEY** 1 Direct Tension Indicator  
2 Nut face washer  
3 Gap

**Assembly configuration for EN 14399-7 Property Class 8.8 with DTI  
Tightened by nut rotation  
Figure 1**

## Use of High Strength Structural Bolting Assemblies for Preloading BS EN 14399-7 PC 8.8 Csk with Direct Tension Indicators (DTI's)

### **Initial Tightening**

The bolt head shall be prevented from rotation using the screwdriver slot in the head and each assembly shall be brought to 'snug tight' condition by nut rotation. The tightening process shall be carried out from bolt to bolt within the group, starting from the most rigid part of the connection and moving progressively towards the least rigid part.

Note: The most rigid part of a cover plate connection of an 'I' section is commonly in the middle of the connection bolt group.

The 'snug tight' condition of a fastener assembly shall be when initial deformation of the DTI protrusions begins. This first step shall be completed for all bolts in one connection prior to commencement of the second step.

### **Final Tightening**


When all the assemblies in a connection have been snug tightened then final tightening can commence. Tightening shall be carried out progressively from the most rigid part of the connection to the least rigid part. Tightening shall continue until the specified indicator gap has been achieved (see Table 1)

<b>Table 1</b>	
<b>Thickness of feeler gauge</b>	
Direct tension indicator position	Thickness of feeler gauge
Under nut, when nut is rotated (Figure 1)	0.25mm

The average specified indicator gap shall be determined using the following measurement procedure; the feeler gauge shall be used as a 'no go' inspection tool. The feeler gauge shall be pointed at the centre of the bolt see Figure 2 and shall refuse to enter the number of refusal spaces specified in Table 2. It is advisable to leave some small gap to prevent accidental overtightening and breakage but if the gap has been completely closed inadvertently this is not considered by Cooper & Turner to be cause for rejection.

<b>Table 2</b>	
<b>Feeler gauge requirements</b>	
Number of indicator protrusions	Minimum number of feeler gauge refusals
4	3
5	3
6	4
7	4
8	5
9	5

## Use of High Strength Structural Bolting Assemblies for Preloading BS EN 14399-7 PC 8.8 Csk with Direct Tension Indicators (DTI's)

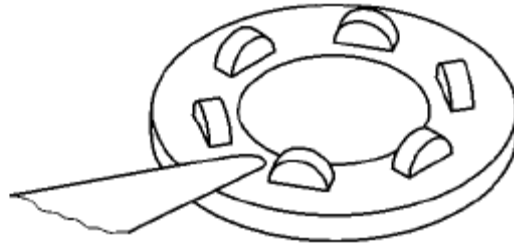

**Figure 2 - Checking the indicator gap (example with six protrusions)**

When the Direct Tension Indicators are installed in accordance with Cooper & Turner's instructions then the shank tension achieved will be in the range shown below.

Nominal bolt diameter	Shank tension kN	
	H8 for 8.8	
	min	max
M16	88	106
M20	137	164
M22 <sup>1</sup>	170	204
M24	198	238
M27 <sup>1</sup>	257	308
M30	314	377
M36	458	550

<sup>1</sup> Non - preferred sizes. Can only be supplied if the quantity required is sufficient to warrant manufacture.